



Review

Legal situation and current practice of waste incineration bottom ash utilisation in Europe



Dominik Blasenbauer^{a,*}, Florian Huber^a, Jakob Lederer^a, Margarida J. Quina^b, Denise Blanc-Biscarat^c, Anna Bogush^d, Elza Bontempi^e, Julien Blondeau^f, Josep Maria Chimenos^g, Helena Dahlbo^h, Johan Fagerqvistⁱ, Jessica Giro-Paloma^g, Ole Hjelm^j, Jiri Hyks^j, Jackie Keaney^k, Maria Lupsea-Toader^c, Catherine Joyce O'Caollai^k, Kaja Orupõld^l, Tadeusz Pająk^m, Franz-Georg Simonⁿ, Lenka Svecova^o, Michal Šyc^p, Roy Ulvang^q, Kati Vaajasaari^r, Jo Van Caneghem^s, Andre van Zomeren^t, Saulius Vasarevičius^u, Krisztina Wégnér^v, Johann Fellner^a

^a Christian Doppler Laboratory for Anthropogenic Resources, Institute for Water Quality and Resource Management, TU Wien, Karlsplatz 13/226, 1040 Vienna, Austria

^b CIEPQPF- Chemical Process Engineering and Forest Products Research Centre, Department of Chemical Engineering, University of Coimbra, Rua Silvío Lima – Polo II, 3030-790 Coimbra, Portugal

^c Univ Lyon, INSA Lyon, DEEP Laboratory (Déchets Eaux Environnement Pollutions), EA 7429, F-69621 Villeurbanne Cedex, France

^d Department of Earth Sciences, University College London, Kathleen Lonsdale Building, 5 Gower Place, London, United Kingdom; Centre for Agroecology, Water and Resilience, Coventry University, Ryton Organic Gardens, Coventry, United Kingdom

^e INSTM and Chemistry for Technologies Laboratory, University of Brescia, Via Branze 38, 25123 Brescia, Italy

^f Thermo and Fluid Dynamics (FLOW), Faculty of Engineering, Vrije Universiteit Brussel (VUB), Pleinlaan 2, 1050 Brussels, Belgium

^g Universitat de Barcelona | UB, Department of Materials Science and Physical Chemistry, C/ Martí i Franquès, 1, 08028 Barcelona, Spain

^h Finnish Environment Institute SYKE, Center for Sustainable Consumption and Production, Latokartanonkaari 11, FI-00790 Helsinki, Finland

ⁱ Avfall Sverige, Baltzarsgatan 25, 211 36 Malmö, Sweden

^j Danish Waste Solutions ApS, Agern Allé 3, DK-2970 Hørsholm, Denmark

^k Indaver Ireland, 4th Floor, Block 1, Old Dunleary Road, CO. Dublin Dun Laoghaire, Ireland

^l Institute of Agricultural and Environmental Sciences, Estonian University of Life Sciences, Kreutzwaldi 5, 51006 Tartu, Estonia

^m AGH University of Science and Technology in Kraków, Department of Power Systems and Environmental Protection Facilities, Al. Mickiewicza 30, 30-059 Krakow, Poland

ⁿ BAM Federal Institute for Materials Research and Testing, Division 4.3 Contaminant Transport and Environmental Technologies, Unter den Eichen 87, 12205 Berlin, Germany

^o Univ. Grenoble Alpes, Univ. Savoie Mont Blanc, CNRS, Grenoble INP, LEPMI, 38000 Grenoble, France

^p Environmental Process Engineering Laboratory, Institute of Chemical Process Fundamentals of AS CR, Rozvojová 135/1, Prague 6, Czech Republic

^q Avfall Norge, Øvre Vollgate 6, 0158 Oslo, Norway

^r REACHLaw Ltd., Vänrikinkuja 3 JK 21, 02600 Espoo, Finland

^s KU Leuven, TC Materials Technology, Group T Campus, Andreas Vesaliusstraat 13, 3000 Leuven, Belgium

^t ECN Part of TNO, P.O. Box 15, 1755 ZG Petten, The Netherlands

^u Vilnius Gediminas Technical University | VGTU, Department of Environmental Protection and Water Engineering, Saulėtekio al. 11, 10223 Vilnius, Lithuania

^v Environmental Advisor, Budapest, Hungary

ARTICLE INFO

Article history:

Received 24 July 2019

Revised 18 November 2019

Accepted 21 November 2019

Available online 11 December 2019

ABSTRACT

Almost 500 municipal solid waste incineration plants in the EU, Norway and Switzerland generate about 17.6 Mt/a of incinerator bottom ash (IBA). IBA contains minerals and metals. Metals are mostly separated and sold to the scrap market and minerals are either disposed of in landfills or utilised in the construction sector. Since there is no uniform regulation for IBA utilisation at EU level, countries developed own rules with varying requirements for utilisation. As a result from a cooperation network between European experts an up-to-date overview of documents regulating IBA utilisation is presented. Furthermore, this

Abbreviations: Al, aluminium; As, arsenic; Ba, barium; Be, beryllium; Cd, cadmium; Co, cobalt; Cr (total), total chromium; Cr (VI), hexavalent chromium; Cu, copper; Hg, Mercury; K, potassium; Mn, manganese; Mo, molybdenum; Na, sodium; Ni, nickel; Pb, lead; Sb, antimony; Se, selenium; Sn, tin; Ti, titanium; Tl, tellurium; V, vanadium; Zn, zinc; BTX, benzene, toluene, xylene; BTEX, benzene, toluene, ethylbenzene, xylene; EOX, extractable halogens inorganic bonding; PAH, polycyclic aromatic hydrocarbon; PCB, polychlorinated biphenyl; PCDD/PCDF, polychlorinated dibenzodioxins/-furans; cf., Latin: cōfer (English: compare); COD, chemical oxygen demand; CPR, construction products regulation; C&D, construction and demolition; DM, dry matter; DOC, dissolved organic carbon; EoW, end of waste; EU, European union; FBC, fluidised bed combustion; GF, grate furnace; HP, hazardous properties; IBA, incinerator bottom ash; LNEC, laboratório nacional de engenharia civil; LOI, loss on ignition; LoW, list of waste; LV, limit value; MIBA, mineral fraction from incinerator bottom ash; MSWI, municipal solid waste incineration; perc., percolation test; POPs, persistent organic pollutants; RK, rotary kiln; TOC, total organic carbon; TEQ, toxic equivalent; VOC, volatile organic compounds; vol.%, volume-percent; wt.%, weight-percent.

* Corresponding author.

E-mail address: dominik.blasenbauer@tuwien.ac.at (D. Blasenbauer).

<https://doi.org/10.1016/j.wasman.2019.11.031>

0956-053X/© 2019 The Authors. Published by Elsevier Ltd.

This is an open access article under the CC BY license (<http://creativecommons.org/licenses/by/4.0/>).

Keywords:

Municipal solid waste incineration
 Incinerator bottom ash
 Utilisation
 Legal requirements
 European Union
 legal situation

work highlights the different requirements that have to be considered. Overall, 51 different parameters for the total content and 36 different parameters for the emission by leaching are defined. An analysis of the defined parameter reveals that leaching parameters are significantly more to be considered compared to total content parameters. In order to assess the leaching behaviour nine different leaching tests, including batch tests, up-flow percolation tests and one diffusion test (monolithic materials) are in place. A further discussion of leaching parameters showed that certain countries took over limit values initially defined for landfills for inert waste and adopted them for IBA utilisation. The overall utilisation rate of IBA in construction works is approximately 54 wt%. It is revealed that the rate of utilisation does not necessarily depend on how well regulated IBA utilisation is, but rather seems to be a result of political commitment for IBA recycling and economically interesting circumstances.

© 2019 The Authors. Published by Elsevier Ltd. This is an open access article under the CC BY license (<http://creativecommons.org/licenses/by/4.0/>).

1. Introduction

About 20–25 wt% of the waste input to incineration is transferred to so-called incinerator bottom ash (IBA), which represents the major solid residue from municipal solid waste incineration (MSWI) (Brunner and Rechberger, 2015; Morf et al., 2000). This secondary waste is roughly composed of a mineral fraction (80–85 wt%), metals (ferrous 7–10 wt%; non-ferrous 1–5 wt%) and a minor fraction of unburned material (<1 wt%) (CEWEP, 2016; Chandler et al., 1997; Chimenos et al., 1999; Holm and Simon, 2017; Huber et al., 2019). The term *metal* is to be understood in the present article as pieces of metals with an oxidation state of 0, which can be separated from the bulk of bottom ash. Chemical compounds like iron oxides present in the mineral fraction are not considered as *metals* in the present article. Due to their economic value (Verbinnen et al., 2017), metals are recovered and subsequently recycled in the metal industry (Allegrini et al., 2014; Bunge, 2018; Gökelma et al., 2019; Holm and Simon, 2017; Kahle et al., 2015; Lamers, 2015; Nørgaard et al., 2019; Van Caneghem et al., 2019; Vehlow and Bourtsalas, 2019). Conventional processes are able to recover about 85–95 wt% of the ferrous metals and 40–65 wt% of the non-ferrous metals present in IBA (Bunge, 2018). While the recycling of metals is common practice, the mineral fraction is either disposed of in landfills (including landfill construction) or utilised in the civil engineering sector as a secondary raw material (Silva et al., 2019; Verbinnen et al., 2017). Unless otherwise stated, in the subsequent text the term *IBA* always refers to unprocessed (*raw*) bottom ash. And in order to avoid confusion the term *MIBA* is introduced. *MIBA* stands for *mineral fraction from IBA*. While some countries utilise up to 100 wt% of *MIBA* in the civil engineering sector, other countries dispose of up to 100 wt% of this residue in landfills (Dou et al., 2017). Such different rates of utilisation may be a consequence of different barriers and/or drivers that can be of technical-, ecological-, economical- or legislative nature. The present work focuses on the latter, since legal aspects are most definitive for the utilisation of *MIBA*.

The European Union (EU) passed rules that form the legal basis for waste management operations. Even though these rules have to be applied by all member states, states can pass their own individual legislation within this framework as long as it is in accordance with EU law. These rules at EU level serve as a reference to minimise the effects on the environment and human health resulting from waste management activities. In the context of IBA handling the following EU rules have to be considered.

The incineration of waste in the EU is harmonised in *Directive 2010/75/EU on industrial emissions* (EU, 2010), which is due to its nature legally binding for all member states and therefore has to be implemented into national law (EU, 2019). If a waste incineration plant is operated in a member state it has to fulfil the minimum requirements set out in this directive. Such requirements are

for example operating conditions that ensure a proper conversion of the waste in such a manner that the resulting bottom ashes show either total organic carbon contents lower than 3 wt% or their loss on ignition is less than 5 wt%. The directive furthermore requires the operator of such a plant to minimise the amount and harmfulness of the residues and to recycle them, where appropriate, on or off site. Prior to recycling, chemical and physical properties and the polluting potential shall be assessed including the determination of the total soluble fraction and soluble fraction of heavy metals. Besides these minimum requirements no more detailed parameters are defined in this directive.

Residues from waste incineration are themselves considered waste and are therefore subject to *Commission Decision 2014/955/EU* (EU, 2014a). In this decision a so-called List of Waste (LoW) is established that defines waste types and classifies waste as hazardous (marked with *) or non-hazardous. Regarding IBA, three entries in the LoW are of main importance: 19 01 02 – *ferrous materials removed from bottom ash*, 19 01 11* – *bottom ash and slag containing hazardous substances* and 19 01 12 – *bottom ash and slag other than those mentioned in 19 01 11*. The last entry means, if it can be proven that it does not contain hazardous substances it can be classified non-hazardous waste. Therefore, IBA has to be tested if it shows any of the 15 hazardous properties (HP) laid down in *Commission Regulation (EU) No 1357/2014* (EU, 2014b) and it has to be assessed if persistent organic pollutants (POPs) are present or exceed concentration levels specified in *Regulation (EC) No 850/2004* (EU, 2004).

For the utilisation of *MIBA* as secondary raw material in the construction sector (either as non-hazardous or as hazardous waste), however, there is no harmonised test method and related limit values at EU level and countries have developed their own rules to regulate this matter. Hence, requirements for utilising vary significantly between countries. Van Gerven et al. (2005) and Crillesen and Skaarup (2006) observed the requirements for utilisation in several European countries and gave an overview on limit values for both total and leaching contents and addressed different leaching test methods. Both studies point out that a harmonisation of test standards, implementation of equal legal requirements for utilisation, development of EU treatment standards and equal standards for environmental protection are needed in order to incentivise *MIBA* utilisation. In a study by Saveyn et al. (2014) EoW criteria for waste derived aggregates (including aggregates from *MIBA*) are investigated for sixteen EU member states. The study summarises leaching limit values in the respective countries and the test methods for assessing them. Liu et al. (2015) focused on Denmark, the Netherlands, the USA, Taiwan and China and partially provides information on utilisation and disposal methods, the respective legal requirements and limit values for total and leaching content for utilisation and/or disposal. Dou et al. (2017) gave a broad overview on *MIBA* utilisation, *MIBA* properties, the environmental impact of *MIBA* utilisation and treatment methods

in many EU countries, several Asian countries, the USA, Canada and Australia. For some of the countries leaching limit values and associated tests are presented. Huber and Fellner (2018) investigated nine European countries concerning legal requirements for MIBA utilisation and they presented limit values for total and leaching content and corresponding leaching tests. Vehlow and Bourtsalaz (2019) showed several limit values and leaching test methods for Germany and Switzerland and quantities of annually generated IBA. The rates of metal recovery and utilisation of minerals are additionally shown for thirteen other EU countries.

These reviewed studies revealed a fragmented picture, highlighting the complex nature of MIBA utilisation in a supranational body of independent states like the EU and associated countries. All of these studies have in common that they are not covering the entire European Union, not all legal requirements are shown and relevant legal documents are not always presented. Furthermore, a comparison and discussion of differences in limit values is largely missing.

The aim of this paper is to provide a holistic view on regulations regarding MIBA utilisation outside of landfills, to aggregate the requirements that have to be met in order to utilise MIBA as secondary construction material and to discuss the similarities and differences of those requirements. Moreover, an outlook is to be given on future potential barriers and drivers which may complicate or facilitate utilisation of MIBA. The geographic system boundary is the entire EU and its neighbouring countries Norway and Switzerland.

Based on these aims the following research questions can be raised: (1) How is the utilisation of MIBA regulated in the observed countries and how much is utilised? (2) Which parameters and requirements have to be met for utilising MIBA and how do they differ between the countries? (3) Which future potential barriers and drivers may complicate or facilitate MIBA utilisation?

2. Methods

To answer questions related to policies in different countries, an expert survey is a suitable and widely applied method (Buchholz et al., 2009; Gabre-Madhin and Haggblade, 2004; Ray, 1999). According to Meuser and Nagel (2009), experts are defined by the knowledge they possess in the targeted field. This “expert knowledge [...] is defined as a special knowledge which the expert is clearly and distinctly aware of” (Meuser and Nagel, 2009). When carrying out a survey with experts, the interviewees should already have or build up a thorough knowledge in the expert's field, in order to present themselves as competent. This is usually dealt with by an in-depth review of literature in the expert's field, carried out before the expert survey is conducted (ibid.). Finally, the collected data from both, literature and expert survey, should be validated and discussed, in order to get a better understanding of possible future policy directions (Wood and Ford, 1993). Therefore, a focus group discussion (FGD) with the experts participating in the survey is carried out (Onwuegbuzie et al., 2009).

To follow these basic methodological steps, the article at hand applies a three-stage mixed methods approach, consisting of a policy review in the first stage, an expert survey in the second stage, and a focus group discussion with the experts in the third and last stage.

2.1. Policy review

The information on municipal solid waste incineration in the 28 EU member states was obtained from the online data base of the Confederation of European Waste-to-Energy Plants (CEWEP) (CEWEP, 2018). The result of this pre-scan indicates that 20 out

of 28 EU members have implemented MSWI. Those countries are namely: Austria, Belgium, Czech Republic, Denmark, Estonia, Finland, France, Germany, Hungary, Ireland, Italy, Lithuania, Luxembourg, the Netherlands, Poland, Portugal, Slovakia, Spain, Sweden and the United Kingdom. Including Norway and Switzerland this makes in total 22 countries that are considered in this study. From these countries, information on the following topics was searched for in the literature databases Google Scholar and Scopus: (1) General questions about MSWI (number of plants, capacity, incineration types) – exemplary search terms: *municipal + solid + waste + incineration + in + 'country name' + capacity + number of MSWI plants*; (2) Policy related questions for MIBA handling – exemplary search terms: *legal + regulation + requirements + incinerator + bottom + ash + utilisation + 'country name'*; (3) Requirements for utilisation of MIBA (limit values) – exemplary search terms: *chemical + composition + incinerator + bottom + ash + leaching + test + 'country name'*; (4) Fields of application for MIBA – exemplary search terms: *incinerator + bottom + ash + utilisation + application + road + cement + building + material + recycling + 'country name'*; (5) Current practice of MIBA utilisation (utilisation rate) – exemplary search terms: *incineration + bottom + ash + utilisation + rate + 'country name'*; By using Google Translator it was possible to extend the research to sources in all respective national languages from the investigated countries.

2.2. Questionnaire survey with experts

Based on the policy review, a questionnaire was designed and experts in each country under consideration were approached to participate in the survey. Where possible, these experts were selected from the COST action *Mining the European Anthroposphere (MINEA)* (MINEA, 2019). The MINEA project assesses anthropogenic resources like MIBA with respect to their potential to produce secondary raw materials by building up a network of competent persons (experts) for data collection and interpretation (Lederer et al., 2017). If a country was not represented in the MINEA expert group, additional experts were found (from scientific and policy literature) and added to the list. The final list of experts on MIBA utilisation, which included overall 29 specialists from scientific institutions, plant operators, waste management consultants, professionals from environmental agencies and experts on waste policy, is presented in Fig. 1.

2.3. Focus group discussion with survey participants

The questionnaires were analysed, compiled, and the results subsequently presented in a workshop on 26th and 27th November 2018 in Budapest, with a number of participants in the expert survey being present (Austria, Denmark, Czech Republic, Estonia, France, Germany, Lithuania, Portugal, Slovakia, Spain and the United Kingdom). Furthermore, additional experts participated in the presentation. These additional experts are affiliated to European scientific institutions, consultant firms and representatives from waste incineration plant operators. The presentation itself was used as a narrative-generating input for the focus group discussion that followed the presentation, aiming to get feedback and validation on the status of data collection and possible future directions of MIBA utilisation as construction material from a policy perspective.

2.4. Analysis of parameters and limit values

2.4.1. Determination of the utilisation rate

The utilisation rate u_n of MIBA outside of landfills in country n is determined in two different ways: (a) it is taken as reported in literature or by the participating experts or (b) it has to be calculated

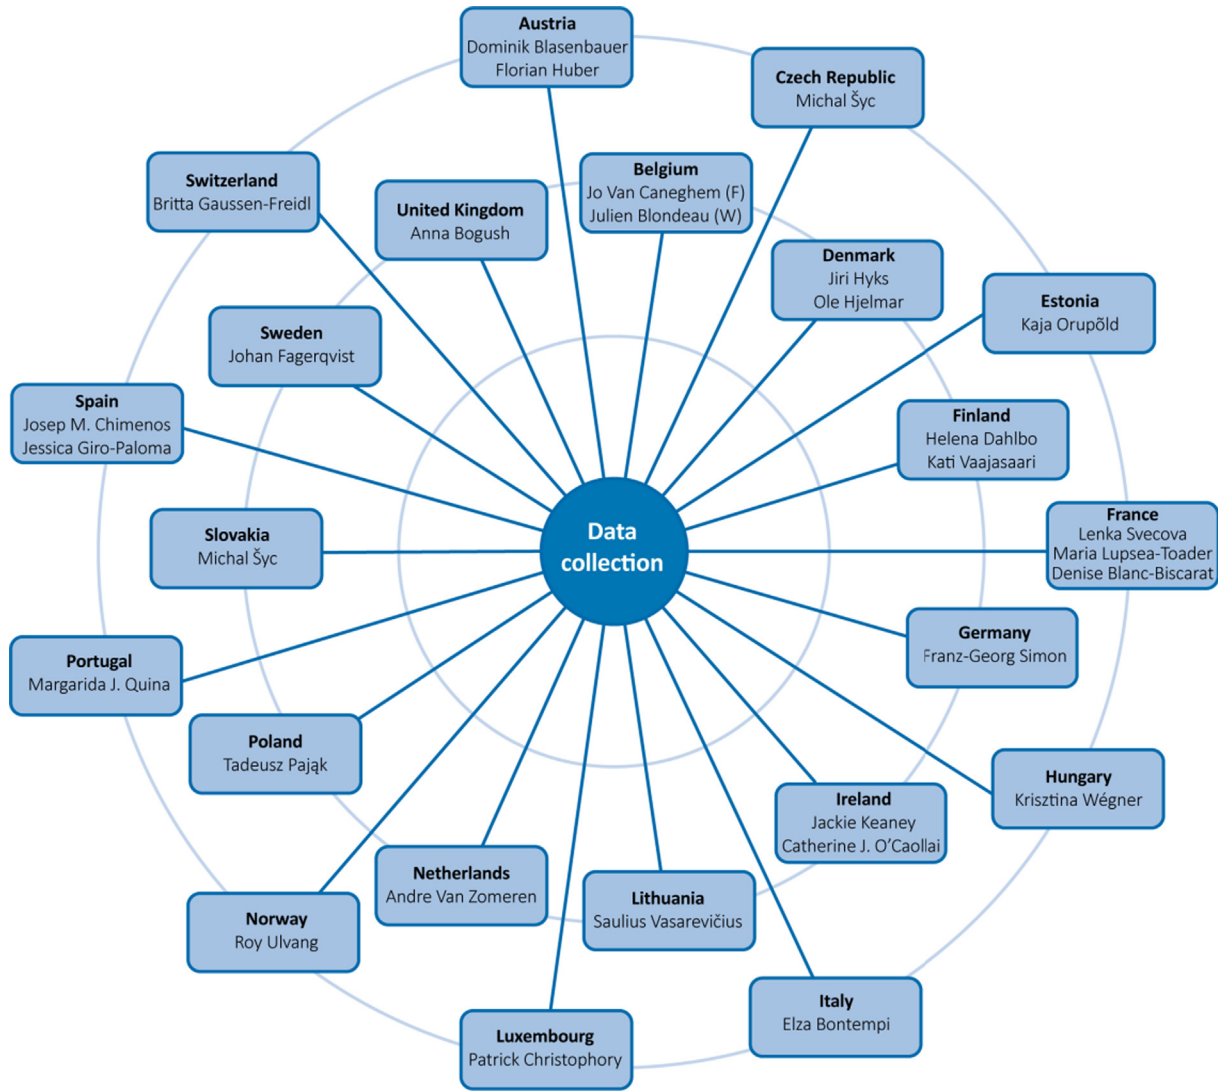


Fig. 1. Expert network of participating specialists from scientific institutions, plant operators, waste management consultants, professionals from environmental agencies and experts on waste policy.

from reported mass flows. Either way, u_n is a ratio between the mass of MBA that is utilised outside of landfills $m_{u,n}$ and the total generated MBA mass $m_{g,n}$ in the respective country.

$$u_n = \frac{m_{u,n}}{m_{g,n}} [(Mt/a)/(Mt/a)] \quad (1)$$

It must be noted that $m_{g,n}$ is the mass of MBA reported for each country. However, it is not always clear whether the MBA mass reported is MBA as generated in the furnace or if some partial metal separation either directly in the MSWI plant or at other facilities has taken place. This leads to some uncertainty of the data.

2.4.2. Determination of relevance levels for parameters

For the determination of the relevance of a specific parameter x (e.g. elements, compounds, lumped parameters such as TOC), a so-called relevance level r_x is calculated. r_x (illustrated in Equation (2)) is defined as a ratio between $\sum y_{x,n} m_{g,n}$ and m_R . The numerator in Equation (2) is the sum of the MBA mass generated in all countries that defined a limit value for a particular parameter. For every country n , the mass of MBA generated (variable $m_{g,n}$) is multiplied by a factor $y_{x,n}$ that indicates if the observed parameter x is defined

in country n . $y_{x,n}$ can be either 0 if the parameter is not defined or 1 if the parameter is defined. Finally, all these products from the single countries (being either 0 or $m_{g,n}$) are added. The denominator in Equation (2) represents the total generated mass m_R of MBA in all countries where MBA utilisation is regulated and according requirements for utilisation are known.

$$r_x = \frac{\sum y_{x,n} m_{g,n}}{m_R} [(Mt/a)/(Mt/a)] \quad (2)$$

The calculation of the relevance level is carried out for all parameters defined in the observed countries.

2.4.3. Comparison of leaching limit values between countries

As it is not practical to compare leaching limit values directly due to their different testing methods, a common base line has to be found. This common base line is the EU leaching requirements for disposing of material in landfills for inert waste – Table 1. Although these types of landfills are (1) not intended for disposing of incineration residues and (2) criteria for landfilling material are based on completely different scenarios than using material in constructions (e.g. different protection levels, consideration of differ-

Table 1
Limit values for acceptance at landfills for inert waste (EU, 2003).

Liquid to solid ratio [l/kg]	EU landfill for inert waste		
	batch tests		percolation test
	2	10	0.1
Unit	mg/kg	mg/kg	mg/l
As	0.1	0.5	0.06
Ba	7	20	4
Cd	0.03	0.04	0.02
Cr (total)	0.2	0.5	0.1
Cu	0.9	2	0.6
Hg	0.003	0.01	0.002
Mo	0.3	0.5	0.2
Ni	0.2	0.4	0.12
Pb	0.2	0.5	0.15
Sb	0.02	0.06	0.1
Se	0.06	0.1	0.04
Zn	2	4	1.2
Chloride	550	800	460
Fluoride	4	10	2.5
Sulphate	560	1,000	1,500
Phenol index	0.5	1	0.3
DOC	240	500	160
TDS	2,500	4,000	–

ent time frames for landfilling and constructions), the following paragraphs will illustrate why this is still an appropriate choice. The compliance with limit values for inert waste landfills can be determined either by the test methods *batch test* at liquid to solid ratio 2 or 10 l/kg and *percolation test* at liquid to solid ratio 0.1 l/kg (EU, 2003). Hence, specific limit values for these three tests were established for inert waste landfills. These limit values were assumed to result in equal protection levels for soil and groundwater. The test methods correspond to the leaching test methods EN 12457/1–4 and EN 14405, which are in place in the investigated countries. This equivalence allows a normalisation of the leaching limit values for utilisation and makes it possible to compare utilisation limit values even when they have to be assessed with different liquid to solid ratios.

The normalised limit value is called N . N is defined as a ratio between the leaching limit value $c_{x,u,n}$ of a specific parameter x defined for utilisation in country n and the leaching limit value $c_{x,l,EU}$ defined for landfilling inert waste according to the EU landfill directive:

$$N = \frac{c_{x,u,n}}{c_{x,l,EU}} [(mg/kg)/(mg/kg)] \quad (3)$$

This procedure is illustrated by the following numerical example, using Eq. (3): Assuming the limit value for utilisation of MIBA for the element $x = As$ in the leachate in country $n = France$ is $c_{As,u,n} = 0.6$ mg/kg. To assess the leaching behaviour of MIBA, *France* demands using testing procedure EN 12457-2 (batch test, liquid to solid ratio 10 l/kg). In Table 1, column two (batch test, 10 l/kg) the limit value for the element $x = As$ is 0.5 mg/kg. Hence, the ratio of N equals to 1.2 (0.6 mg/kg / 0.5 mg/kg). This means the limit value for *As* in *France* is a factor 1.2 higher than the limit for inert waste landfills (according to the EU landfill directive).

However, this does not imply that the environment is less protected in case of application as construction material due to the substantial differences in the scenarios of application (application in construction versus landfilling). The calculated values N can be used as an indicative comparison of limit values between investigated countries.

This calculation of N is only carried out for countries (and fields of application) that (a) defined leaching limit values, and (b) have

leaching tests (including a liquid to solid ratio) in use that corresponds to the ones given in Table 1.

3. Results and discussion

3.1. How is the utilisation of MIBA regulated in the observed countries and how much is utilised?

In the EU, Norway and Switzerland 463 municipal solid waste incineration (MSWI) plants are operated (see Table 2). These plants can incinerate approximately 90 Mt/a municipal solid waste and industrial waste of similar composition. From this waste input 17.6 Mt/a are transferred into IBA. These correlate to approximately 20 wt% of the annual incineration capacity in these countries. It can be seen that the majority (16) of the 22 observed countries permit the utilisation of MIBA outside of landfills. But only eleven are making use of this permit and utilise MIBA in practice. In those countries where MIBA utilisation is practiced, the utilisation rate for MIBA varies between 20 and 100 wt%. Approximately 54 wt% of the entire generated MIBA in the EU, Norway and Switzerland has been utilised outside of landfills between 2015 and 2019.

Table 2 summarises relevant documents that regulate MIBA utilisation outside of landfills. The majority of countries regulate MIBA utilisation on the basis of legislation (decrees, regulations, and ordinances). Only Austria, Germany, Sweden and the United Kingdom published guidelines that address specific utilisation methods. Guidelines are unlike legislation usually not legally binding as they are considered to be so-called *soft law* (Eurofound, 2011; OECD, 2019). Portugal has an individual permit in place, issued by the independent national body *Laboratório Nacional de Engenharia Civil (LNEC)*, for one IBA processing company. In six countries, namely Estonia, Hungary, Ireland, Luxembourg, Norway and Slovakia, the utilisation outside of landfills is not regulated. This is as well the case for the Brussels Capital Region in Belgium and sixteen out of seventeen Spanish autonomous communities (except Catalonia). In the case of Estonia, Hungary, Ireland, Luxembourg, Slovakia, Brussels Capital Region and Spain (except Catalonia) there is no regulation in place; in Norway utilisation outside of landfills is not allowed. All these countries (or regions) with no regulations regarding MIBA utilisation have in common, that the quantity of IBA is relatively small (ranging from 28,000 to 250,000 t/a). Although there are no regulations in place for MIBA utilisation inside Ireland and Luxembourg, both allow the export of the generated IBA. In Ireland one of the two plant operators exports its IBA to the Netherlands for utilisation, whereas the only plant operator in Luxembourg exports its IBA to Germany for utilisation. In Estonia, Hungary, Norway and Slovakia MIBA is disposed of in landfills.

Despite the fact that the utilisation is regulated in such different manner, it cannot be concluded that clear rules automatically results in high utilisation rates. On the one hand, in Lithuania and Switzerland the utilisation of MIBA outside of landfills is clearly regulated but the utilisation rate is still 0 wt%. In Portugal and the United Kingdom, on the other hand, no such clear regulations are in place, but both countries show utilisation rates of 56 wt% and 99 wt%, respectively. Low utilisation rates may be a result of different issues. Such issues can be if: (1) limit values are simply too strict, that IBA cannot comply with (e.g. Switzerland), (2) when the regulative has recently come into force that it takes some time until potential scepticism towards the material is decreased (e.g. Finland), (3) companies do not have experience in using a secondary raw material like MIBA for construction purposes (e.g. Lithuania) and (4) there is no scarcity of primary raw

Table 2

Overview on number and incineration capacity of MSWI plants, annually generated amount of IBA in the observed countries, information if utilisation is permitted and practiced, how much MIBA is utilised, respective documents regulating the utilisation of MIBA in the observed countries, type of legal document and references. (-) . . no data available.

Country	MSWI plants		IBA mass [Mt/a]	MIBA utilisation		MIBA utilisation rate outside landfills [wt.%]	Reference for utilisation rates	Original title of document regulating MIBA utilisation outside of landfills	Type	Reference for documents
	No [-]	Capacity [Mt/a]		permitted	practised					
<i>Austria</i>	11	2.6	0.53	yes	no	0	(Republic of Austria, 2017a)	Bundesabfallwirtschaftsplan 2017; Technische Grundlagen für den Einsatz von Abfällen als Ersatzrohstoffe in Anlagen zur Zementerzeugung	guidance	(Republic of Austria, 2017a, b)
<i>Belgium</i>	15	3.3	0.47	<u>Flanders</u> : yes <u>Wallonia</u> : yes (mandatory) <u>Brussels capital region</u> : not regulated	yes	69	(Bogush, 2018)	VLAREMA-2012 (Flanders); Arrêté du Gouvernement wallon, 14/06/2001 (Wallonia)	legislation	(Flemish Government, 2012 ; Government of Wallonia, 2001)
<i>Czech Republic</i>	4	0.65	0.2	yes	no	0	(Šyc, 2018)	Vyhláška č. 294/2005 Sb. Order N.1672 (2016)	legislation	(Czech Republic, 2005)
<i>Denmark</i>	24	3.7	0.6	yes	yes	99	(Hykš, 2016)	–	legislation	(Kingdom of Denmark, 2016)
<i>Estonia</i>	1	0.25	0.058	not regulated	–	0	–	–	–	–
<i>Finland</i>	9	1.6	0.3	yes	yes	20	(Rantsi, 2018)	Government Decree on the Recovery of Certain Wastes in Earth Construction (843/2017)	legislation	(Government of Finland, 2017)
<i>France</i>	126	14.7	2.9	yes	yes	80	(Tegelbeckers et al., 2015)	Arrêté du 18 novembre 2011 relatif au recyclage en technique routière des mâchefers d'incinération de déchets non dangereux NOR: DEVP1131516A	legislation	(French Republic, 2011)
<i>Germany</i>	68	19.8	4.8	yes	yes	30	(Alwast and Riemann, 2010 ; Mesters, 2018)	LAGA M19 (annex 6) and LAGA M20 (for leachates)	guidance	(LAGA, 1994, 1995)
<i>Hungary</i>	1	0.42	0.12	not regulated	no	0	–	–	–	–
<i>Ireland</i>	2	0.8	0.14	not regulated	no	0 (partial export)	–	–	–	–
<i>Italy</i>	39	6.1	1.03	yes	yes	85	(Utilitalia, 2019)	Decreto 5 febbraio 1998 including its amendment Decreto 5 aprile 2006, n. 186	legislation	(Italian Republic, 1998, 2006)
<i>Lithuania</i>	1	0.28	0.075	yes	no	0	–	Įsakymas 2016 November 25 No. D1-805	legislation	(Lithuanian Government, 2016)
<i>Luxembourg</i>	1	0.17	0.028	not regulated	no	0 (full export)	–	–	–	–
<i>Netherlands</i>	12	7.6	1.9	yes (mandatory)	yes	100	(Born, 2018)	Regeling van 13 december 2007, nr. DJZ2007124397, houdende regels voor de uitvoering van de kwaliteit van de bodem (Regeling bodemkwaliteit)	legislation	(Government of the Netherlands, 2007)
<i>Norway</i>	18	1.8	0.25	not permitted	no	0	–	–	–	–
<i>Poland</i>	6	0.97	0.21	yes	yes	60	(Pająk, 2019)	Poz. 796 – Rozporządzenie Ministra Środowiska z dnia 11 maja 2015 r. w sprawie odzysku odpadów poza instalacjami i urządzeniami	legislation	(Republic of Poland, 2015)
<i>Portugal</i>	4	1.3	0.22	yes	yes	56	(Valorsul, 2017)	Individual permit issued by independent national body (LNEC – Laboratório Nacional de Engenharia Civil))	individual permit	(Valorsul, 2017)
<i>Slovakia</i>	2	0.29	0.062	not regulated	no	0	–	–	–	–
<i>Spain</i>	10	2.4	0.44	<u>Catalonia</u> : yes <u>Rest of Spain</u> : not regulated	yes	58	(Chimenos, 2018)	Ordre de 15 de febrer de 1996 (Catalonia)	legislation	(Generalitat de Catalunya, 1995)
<i>Sweden</i>	34	5.4	0.99	yes	no	0	(Fagerqvist, 2019 ; Van Praagh et al., 2018)	Återvinning av avfall i anläggningsarbeten Handbok	guidance	(Naturvårdsverket, 2010)
<i>Switzerland</i>	30	3.7	0.82	yes	no	0	(Holm and Simon, 2017)	Verordnung über die Vermeidung und Entsorgung von Abfällen (VVEA)	legislation	(Swiss Federal Council, 2015)
<i>United Kingdom</i>	45	12	1.5	yes	yes	99	(Lederer et al., 2018)	Guidance – Use of unbound municipal Incinerator Bottom Ash Aggregate (IBAA) in construction activities: RPS 206	guidance	(United Kingdom, 2019)
Total	463	90	17.6	16	11	54 (or 9.6 Mt/a)	–	–	–	–

Table 3

Parameters for total and leaching content and other requirements that have to be considered in order to utilise MIBA in the permitted fields of application. Related limit values are given in the supplementary information in Tables S1–S5. “non-hazardous waste” means only IBA classified as non-hazardous waste (EU waste code 19 01 12) is allowed to be used. Only countries where MIBA utilisation is regulated are considered in this table.

Country	Parameters specifically defined for MIBA	Permitted field of application	Requirements on		
			total content	leaching content	other requirements
Austria	yes	base layer in road construction (bound and unbound)	Cd, Cr (total), Ni, Pb, TOC	As, Cr (total), Cu, Mo, Ni, Pb, Sb, chloride, sulphate, pH	ferrous metals < 1 wt% DM, non-ferrous metals < 0.8 wt%;
	no	secondary raw material in cement production	As, Cd, Co, Cr (total), Hg, Ni, Pb, Sb, TI	no requirements	Limitations regarding POPs according to (EU, 2004);
Belgium	no	<u>Flanders</u> : bound and unbound construction material	As, Cd, Cr (total), Cu, Hg, Ni, Pb, Zn, asbestos, benzene, ethylbenzene, styrene, toluene, xylene, benzo(a)anthracene, benzo(a)pyrene, benzo(ghi)perylene, benzo(b)fluoranthene, benzo(k)fluoranthene, chrysene, phenanthrene, fluoranthene, indeno(1,2,3-cd)pyrene, naphthalene, hexane, heptane, petroleum, octane, PCB	As, Cd, Cr (total), Cu, Hg, Ni, Pb, Zn	floating contaminants < 5 cm ³ /kg DM, non-floating contaminants < 1 wt% and glass content < 2 wt%;
	yes	<u>Wallonia</u> : Certification test (base layer and hydraulic bound material)	petroleum, PCB, BTEX, EOX, PAH	Al, As, Cd, Co, Cr (total), Cr (VI), Cu, Hg, K, Mo, Ni, Pb, Sb, Ti, Zn, chloride, cyanide, fluoride, sulphate	none
	yes	<u>Wallonia</u> : Regular quality assurance test (base layer and possibly hydraulic bound material)	petroleum, EOX	Al, As, Cd, Co, Cr (VI), Cu, Hg, Mo, Ni, Pb, Sb, Ti, Zn, chloride, cyanide, fluoride, sulphate, nitrate, ammonium, pH, electric conductivity	no requirements
Czech Republic	no	application of waste on soil surface	As, Cd, Cr (total), Hg, Ni, Pb, V, hydrocarbons (C10–40), PCB, BTX, EOX, PAH	no requirements	none
Denmark	no	<u>Category 1</u> : unrestricted use in specific construction applications (no MIBA will meet Cat. 1 requirements), <u>Category 2&3</u> : subbase layer in road construction	As, Cd, Cr (total), Cr (VI), Cu, Ni, Pb, Zn	As, Ba, Cd, Cr (total), Cu, Hg, Mn, Na, Ni, Pb, Se, Zn, chloride, sulphate	non-hazardous waste
Finland	yes	road covered or paved, field covered or paved, subgrade filling in industrial and storage building	no requirements	As, Ba, Cd, Cr (total), Cu, Hg, Mo, Ni, Pb, Sb, Se, V, Zn, chloride, fluoride, sulphate, DOC	non-hazardous waste, particle size < 50 mm;
France	yes	<u>Type 1</u> : maximum 3 m high sublayers of pavements or shoulders of paved road structures, <u>Type 2</u> : maximum 6 m high road embankment or shoulder infrastructures, under the condition to be covered road structures	TOC, hydrocarbons (C10–40), PCB (sum of 28, 52, 101, 118, 138, 153, 180), BTEX, PAH, TEQ	As, Ba, Cd, Cr (total), Cu, Hg, Mo, Ni, Pb, Sb, Se, Zn, chloride, fluoride, sulphate, total dissolved solids	maturation, separation of unburnt material and large metals;
Germany	yes/no ³	<u>Z2</u> : base course below non-permeable top layer, bound base course below low permeable top layer, bound top layer, anti-noise- and visual protection barriers and foundation of road dams with precipitation protection	Cd, Cr (total), Cu, Ni, Pb, Zn, TOC, PCDD/PCDF, EOX	Cd, Cr (total), Cu, Hg, Ni, Pb, Zn, chloride, sulphate, pH, electric conductivity	maturation > 3 months
Italy	yes	road foundation, cement process, construction of embankments, environmental recoveries	no requirements	As, Ba, Be, Cd, Co, Cr (total), Cu, Hg, Ni, Pb, Se, V, Zn, chloride, cyanide, fluoride, sulphate, nitrate, asbestos, chemical oxygen demand, pH	non-hazardous waste
Lithuania	yes	road, foundation of buildings	TOC, loss on ignition	Cd, Cr (total), Cu, Hg, Ni, Pb, Zn, chloride, cyanide, sulphate, pH, electric conductivity	non-hazardous waste
Netherlands	no	bound and unbound construction material,	benzene, ethylbenzene, toluene, xylene,	As, Ba, Cd, Co, Cr (total), Cu, Hg, Mo,	none

Table 3 (continued)

Country	Parameters specifically defined for MIBA	Permitted field of application	Requirements on		
			total content	leaching content	other requirements
		IBC construction material	benzo(a)anthracene, benzo(a)pyrene, benzo(ghi)perylene, benzo(k)fluoranthene, indeno(1,2,3-cd)pyrene, petroleum, PCB (sum of 28, 52, 101, 118, 138, 153, 180), PAH, asbestos	Ni, Pb, Sb, Se, Sn, V, Zn, bromide, chloride, fluoride, sulphate	
Poland	yes	subbase layer in road construction	TOC, hydrocarbons (sum of C10-40), PCB, BTEX, PAH	As, Ba, Cd, Cr (total), Cu, Hg, Mo, Ni, Pb, Sb, Se, Zn, chloride, fluoride, sulphate, phenol index, dissolved organic carbon, total dissolved solids	non-hazardous waste, separation of light impurities, unburnt material, ferrous and non-ferrous metals and maturation, compliance with PL EN 13242 and Technical requirement WT4 "Unbound mixes for national roads" (Republic of Poland, 2015);
Portugal	no	aggregates for unbound and hydraulically bound materials for use in civil engineering work and road construction	<u>Based on individual permit from LNEC:</u> no requirements	<u>Based on individual permit from LNEC</u> ^b : As, Ba, Cd, Cr (total), Cu, Hg, Mo, Ni, Pb, Sb, Se, Zn, chloride, fluoride, sulphate, dissolved organic carbon, total dissolved solids	<u>Based on individual permit from LNEC:</u> compliance with NP EN 13242:2002 + A1:2010
Spain	yes	<u>Catalonia</u> : road subbase, levelling of terrain and embankments, filling and restoration of degradable areas from extractive activities, others	loss on ignition, unburnt material	As, Cd, Cr (VI), Cu, Pb, Zn, total dissolved solids	none
Sweden	no	general use – unbound material	As, Cd, Cr (total), Cu, Hg, Ni, Pb, Zn, PAH low ring number, PAH medium ring number, PAH high ring number	As, Cd, Cr (total), Cu, Hg, Ni, Pb, Zn, chloride, sulphate	none
Switzerland	no	use of waste as raw material and raw meal correction material in the cement industry	As, Cd, Co, Cr (total), Cu, Hg, Ni, Pb, Sb, Sn, Tl, Zn, TOC, hydrocarbons (sum of C5-10), hydrocarbons (sum C10-40), benzene, benzo(a)pyrene, PCB, BTEX, PAH, VOC	no requirements	none
	no	use of waste as grinding additives and aggregates in the cement industry	As, Cd, Cr (total), Cr (VI), Cu, Hg, Ni, Pb, Sb, Zn, TOC, hydrocarbons (sum of C5-10), hydrocarbons (sum C10-40), benzene, benzo(a)pyrene, PCB, BTEX, PAH, VOC	no requirements	none
United Kingdom	no	road, construction of structural platforms, pipe bedding	individual decision	individual decision	non-hazardous waste, compliance with BS EN 13242:2013;

^a Total content limit values are not directly addressing MIBA utilisation, whereas the leaching limit values are specifically addressing MIBA utilisation.

^b MIBA has to comply with leaching limit values for Portuguese non-hazardous waste landfill (Portuguese Republic, 2009).

materials, there is less need for secondary raw materials like MIBA (e.g. Austria).

3.2. Which parameters and requirements have to be met for utilising MIBA and how do they differ between the countries?

Table 3 summarises parameters defined in the documents shown in Table 2. It can be seen that in around half of these documents utilisation of IBA is directly addressed (or these documents were specifically created for that purpose) and therefore parameters are defined accordingly, whereas the others address the recycling of different materials in general. The latter do not differentiate between recycling of soil for example and recycling of MIBA; for both the same parameters and limit values apply. The most commonly permitted utilisation method is the application of MIBA in road construction, followed by different forms of earth works (anti-noise barriers, levelling of terrain, etc.), cement process, use in bound and unbound form and for foundations of structures. The requirements that have to be met in order to utilise MIBA are mainly chemical and/or physicochemical parameters and other requirements such as classification as non-hazardous waste, maximum particle size, maximum content of ferrous and non-ferrous metals etc. Overall 51 different chemical and physicochemical parameters for the total content and 36 for the leaching content are defined in the observed states. Each parameter is characterized by a limit value, which is given in the supplementary information (Tables S1–S5). A detailed view on the data shows that if a country allows the utilisation in road construction or some application where precipitation potentially may reach the layer where MIBA is applied, the focus is on the leaching behaviour of MIBA as soluble components can be released to the environment. If a country allows the use of MIBA in a more general application in bound or unbound form and is not just limiting it to road construction, requirements for the total content become additionally important. In order to limit the dispersion of pollutants (heavy metals, POPs etc.), Austria and Switzerland defined specific limit values for utilisation of IBA in the cement process. If MIBA serves as replacement of primary raw material in the cement kiln, leaching behaviour can be neglected and the total content of volatile components (such as Hg) comes into focus. This can be seen for instance in Italy where the leaching behaviour does not have to be assessed if MIBA is used in the cement manufacturing process. If MIBA is used as grinding additive or aggregate after the cement kiln and this material is used in constructions, potential pollutants are included in the cement matrix and their leaching is therefore as well significantly decreased. An issue

which concerns all applications where MIBA is used is the demolition of such constructions. Even if all pollutants are bound in the material or due to technical measures leaching is suppressed; when the material becomes construction and demolition (C&D) waste it may become subject to legislation specifically addressing C&D waste. Therefore, pollutants from MIBA present in construction materials could prevent or limit the recycling of this material in a second life phase.

In order to assess the leaching behaviour, different standardised test methods are in place. Yet again, a big variation between countries can be observed. Table 4 shows all nine leaching tests which are in use in the countries investigated. Leaching tests differ in the test setup, liquid to solid ratio, the particle size of the tested material and the test duration. The setup can be a batch test (or sometimes as well referred to as shaking test) where both the tested material and the solution are in a bottle with fixed liquid to solid ratio and overhead rotated for a defined duration (usually 24 h). This type of test is defined within the standard EN 12457 parts 1, 2, 3 and 4 (EN, 2002a, b, c, 2003). The difference between these four parts lies within the number of leaching steps (one or two-stage batch test), the liquid to solid ratio (2, 8 and 10 l/kg) and/or the particle size of the tested material (<10 mm or < 4 mm). A second type of test setup is the percolation or column test, where the tested material is packed into a column and the leaching solution flows upwards through the packed material. Depending on the liquid to solid ratio, the leachate is collected in defined intervals. Liquid to solid ratios vary between 0.1 and 10 l/kg and 1–10 l/kg. The particle size of the tested material is sometimes not specified but mostly set to <4 mm. The test duration and particle size requirements of these types of tests often represent a compromise between the desire to obtain local equilibrium-like conditions and a wish to minimise testing time and avoid crushing. Recent standardisation developments under the Construction Products Regulation (CPR) have led to a similar percolation test that is suitable for construction products under this regulation (prEN 16637–3) (EN, 2016). A third type of test (NEN 7375:2004) for bound applications such as the use of MIBA as aggregate in concrete is in use in the Netherlands, where a monolith that contains the tested material is placed into water over a period of 64 days and the concentration of elements mobilised (due to diffusion) is measured (NEN, 2004). Samples are taken in defined time intervals, at which the water is changed after each sampling step. In this test the liquid to monolith surface area is relevant rather than the liquid to solid ratio. Also this tank leaching test is now standardised for construction products under the CPR (prEN 16637–2) (EN, 2014).

Table 4
Overview of leaching tests for MIBA utilisation and countries where those tests are in place.

Leaching test	Test setup	Liquid to solid ratio	Particle size	Test duration	Applying Countries
	[–]	[l/kg]	[mm]	[–]	[–]
EN 12457-1 ^a	batch test	2	<4	24 h	Denmark, Poland
EN 12457-2 ^a	batch test	10	<4	24 h	France, Italy, Lithuania, Portugal ^b
EN 12457-3 ^a	batch test	2 & 8 (two-stage test)	<4	24 h	Finland
EN 12457-4 ^a	batch test	10	<10	24 h	Austria, Belgium (Wallonia – regular quality assurance test), Germany, Spain (Catalonia)
CEN/TS 14405	percolation test	0.1–10	not specified	not specified	Finland, Sweden
CMA2/II/A.9.1.	percolation test	0.1–10	<4	not specified	Belgium (Flanders),
NEN 7343:1995	percolation test	0.1–10	<4	not specified	Belgium (Wallonia – certification test)
NEN 7383:2004	percolation test	1–10	<4	not specified	Netherlands
NEN 7375:2004	monolith in water containment	depending on surface area of monolith	not specified	64 days	Netherlands

^a Note: Most countries translated the standard into national versions, e.g. Austria: ÖNORM EN 12457-4, Finland: SFS-EN 12457-3.

^b Based on special permit from LNEC.

3.2.1. Relevance of specific parameters

Fig. 2 and Fig. 3 depict the results of the calculation of the relevance level described in section 2.4.2. It can be seen that the majority of total content parameters show relevance levels below 20 wt%. Levels above 40 wt% can be seen for Cd, Cr (total), Cu, Ni, Pb, Zn, TOC and PAH. The average relevance level for total content parameters is 19 wt%.

A view at the leaching content parameters reveals a different picture. First, the balance is significantly more on the side of inorganics regarding the number of defined parameters – in contrary to the total content. Second, these inorganic parameters show higher relevance levels with 13 being above 50 wt% and nine of them even close to or slightly above 90 wt%. Those nine parameters are Cd, Cr (total), Cu, Hg, Ni, Pb, Zn, chloride and sulphate. The average relevance level for leaching parameters is 42 wt%. This focus on leaching parameters is unsurprising, since it is more relevant to assess whether a substance is soluble/mobile and therefore more likely to affect environmentally sensitive areas such as (ground) waterbodies or soils.

It has to be noted, that this analysis does not imply that other defined parameters with lower relevance levels are less important, since it does not take into account the field of application and circumstances under which the parameters were defined. This analysis should only show how parameters are split up amongst

countries and reveal parameters that are commonly used to evaluate MIBA utilisation. In addition, the limit values do in part have a much wider scope of application than only MIBA. For example, the limit values in the Netherlands cover all mineral materials used in construction, including primary construction materials.

3.2.2. Comparison of leaching limit values

From eighteen parameters defined at EU level for landfills for inert waste (cf. Table 1), twelve correspond to the most common parameters used for limiting the leaching behaviour discussed in the previous paragraphs. Consequently, the normalisation was applied to these twelve parameters. Based on the two criteria (a) and (b) defined in the last paragraph of section 2.4.3 the following countries and fields of application are left for comparison: Austria, Belgium (Wallonia – regular quality assurance test), Denmark (Category 1&2 and 3), Finland (roadway covered, roadway paved and subgrade filling in industrial or storage building, field covered, field paved), France (Type 1 and 2), Germany, Italy, Lithuania, Poland, Portugal, Spain and Sweden. The results of the normalisation procedure are summarised in Table 5.

It can be seen that many cells are coloured yellow, which means that limit values are closely related to the inert landfill limit values. This is specifically the case in Finland for the application “Field covered”, where ten out of twelve parameters are equal to the limit

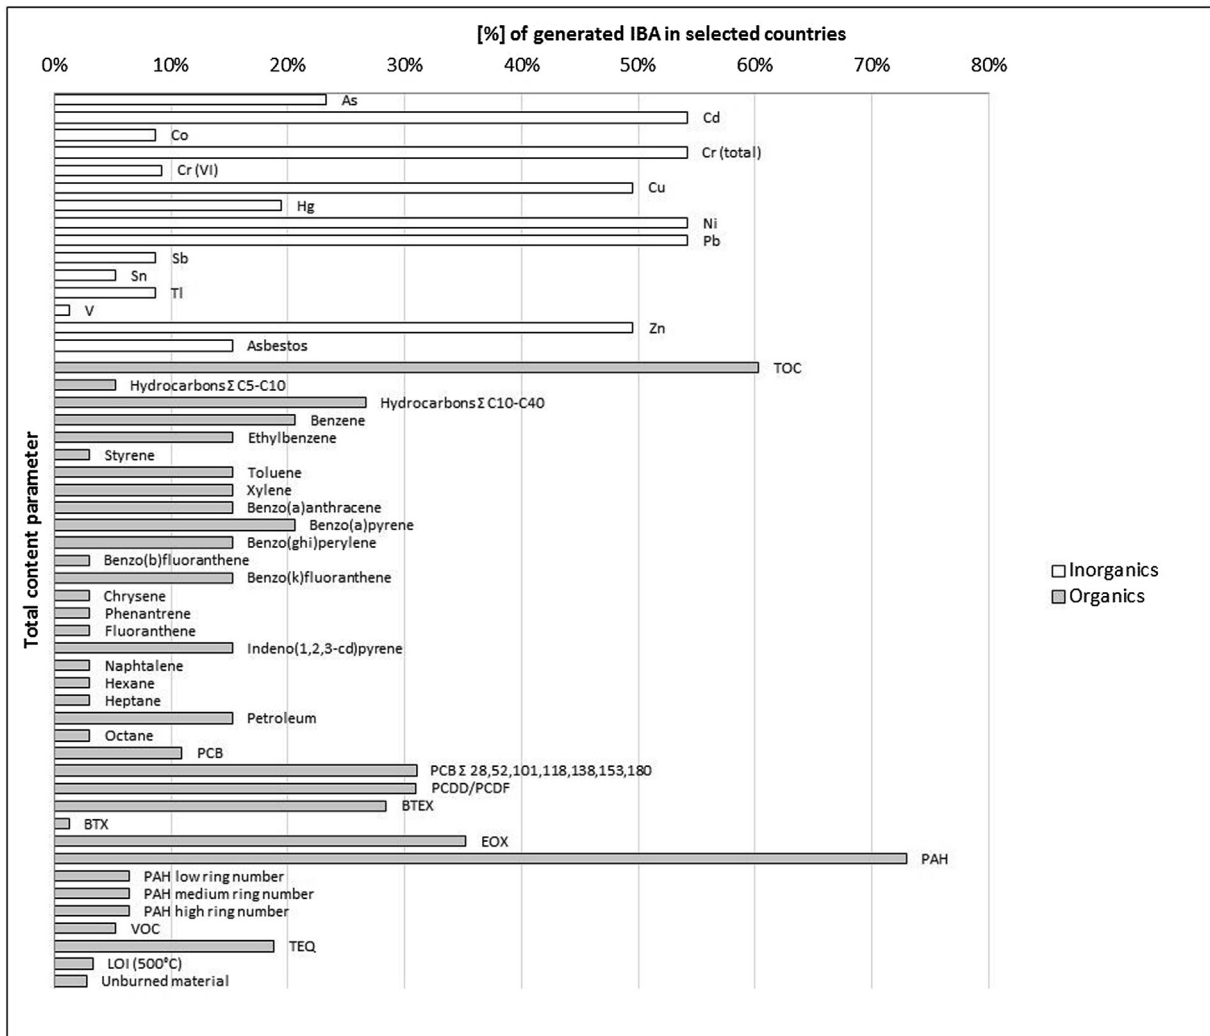


Fig. 2. Relevance of total content parameters relative to the overall generated amount of IBA in Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Italy, Lithuania, Netherlands, Poland, Portugal, Spain, Sweden and Switzerland.

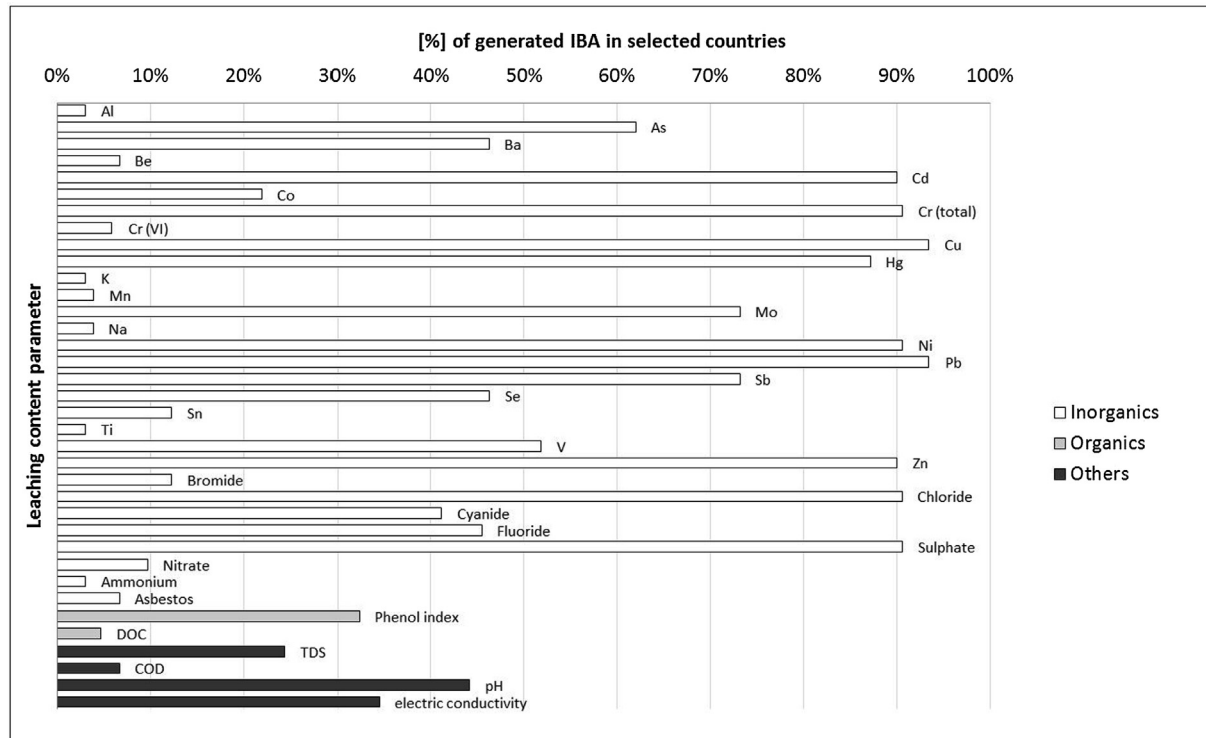


Fig. 3. Relevance of leaching content parameters relative to the overall generated amount of IBA in Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Italy, Lithuania, Netherlands, Poland, Portugal, Spain, Sweden and Switzerland.

values defined for inert landfills at EU level. It is assumed that Polish legislators have also been guided by the inert landfill limits, since eleven out of twelve parameters are exactly two times higher than the inert landfill limit value and the twelfth is equal to the inert landfill limit value. It also becomes obvious that countries that allow a general use as construction material also define the most stringent limit values. Those applications are represented by many green cells per category in the table and are in place in Denmark (Category 1&2) and Sweden (General use – unbound material). The individual permit issued by Portuguese authorities demands compliance with Portuguese non-hazardous waste landfill limit values, and since these limit values are higher than limit values for landfilling inert waste, relatively high factors were determined. Additionally, limit values for non-hazardous waste landfills in Portugal are higher than limit values for non-hazardous waste landfills defined in Council Decision (2003/33/EC) (EU, 2003). Overall, it was found that 16% of all defined leaching limit values for utilisation match exactly the leaching limit values for landfills for inert waste, 16% are stricter and therefore 68% of the values are less strict than the leaching limit values for landfills for inert waste. Breaking down this analysis to the different parameters reveals that in seven out of seventeen cases the limit value for the element Pb matches exactly the limit value for landfills for inert waste. It is followed by Hg (5/17), As and Ni (both 4/17), Cr (total) (3/17), Cd (2/17) and Cu, Mo, Sb, Zn and chloride (all 1/17). Only for sulphate all states defined own limit values. As the main field of application for MIBA is in the construction of roads, an analysis how different countries are defining limit values for that purpose is carried out. By taking into account only countries and applications that allow the use in road construction only and reducing the list of parameters to solely parameters where a value can be found in each category, it is possible to compare how strict values for utilisation in road construction are defined within the countries. This analysis reveals that in comparison

Polish MIBA has to comply with the strictest leaching limit values, followed by Austria, Finland (roadway covered), Denmark (Category 3), France (Type 2), France (Type 1) and Finland (roadway paved).

Even though this analysis reveals a large variation between countries or applications regarding the magnitude of the limit values, one should not draw a conclusion that certain states are handling this matter more and others less carefully. Saveyn et al. (2014) already addressed the similarity between utilisation limit values and landfill limit values – even though the focus was on different waste derived aggregates and not only MIBA. Regardless, this report recommended to rather carry out risk or impact-based assessments for obtaining limit values for a specific field of application, than adopting limit values from other legislation. Such an approach was made by Denmark, Sweden or the Netherlands, for example. An assessment procedure that considers differences in national conditions like soil properties, infiltration, distance to groundwater or different climatic conditions, in combination with a standardised set of parameters and risk or impact-based models, linked to a specific application would create more equal and foreseeable environmental impacts of MIBA utilisation in the member states.

3.3. Which future potential barriers and drivers may complicate or facilitate MIBA utilisation?

Considering the huge amount of IBA produced in the EU (17.6 Mt/a) it would be very relevant to find ecologically suitable applications and avoid the landfill disposal. For this, the main barriers and drivers have to be addressed. A study by Klymko et al. (2017) found out that from 15 HP criteria laid down in Commission Regulation 1357/2014 (EU, 2014b), HP 10 (*Toxic for reproduction*) and HP 14 (*Ecotoxic*) potentially may lead to a classification of IBA as hazardous waste. IBA is seen to be classified hazardous by

Table 5

Comparison of leaching limit values for MIBA utilisation and EU leaching limit values for disposing of in landfill for inert waste. Values = 1: leaching limit value for MIBA utilisation matches exactly limit value for landfill for inert waste (cell colour yellow), values < 1: leaching limit value for MIBA utilisation is stricter than limit value for landfill for inert waste (cell colour yellowish to green), values > 1: leaching limit value for MIBA utilisation is less strict than limit value for landfill for inert waste (cell colour yellowish to red). Cells containing (-): no leaching limit value for MIBA utilisation is defined for the respective parameter. Factors determined for Portugal are based on an individual permit issued by Portuguese authorities. percolation test (perc.); limit value (LV).

	Austria	Belgium (Wallonia)	Denmark	Denmark	Finland	Finland	Finland	Finland	France	France	Germany	Italy	Lithuania	Poland	Portugal	Spain (Catalonia)	Sweden
	Baselayer	Regular quality assurance test (base layer and possibly hydraulic bound material)	Category 1&2	Category 3	Roadway Covered	Roadway Paved and Subgrade filling in industrial or storage building	Field Covered	Field Paved	Type 1	Type 2	Z2	Utilisation	Civil Engineering purposes	Sub-base of roads and highways	Aggregates for unbound and hydraulically bound materials for use in civil engineering work and road construction	Road subbase, Levelling of terrain and embankments, Filling and restoration of degradable areas from extractive activities, others	Less than little risk (general use) - unbound material
As	1	2	0.16	1	2	4	1	3	1.2	1.2	-	1	-	2	10	2	0.18
Cd	-	25	0.13	2.7	1	1.5	1	1.5	1.3	1.25	13	1.3	0.75	2	30	25	0.5
Cr (total)	1	-	0.1	5	4	20	1	10	4	2	4	1	4	2	40	-	2.4
Cu	2	10	0.1	4.4	5	5	1	5	25	25	1.5	0.25	0.75	2	25	10	0.4
Hg	-	20	0.067	0.67	3	3	1	3	1	1	1	1	0.1	2	50	-	0.5
Mo	2	3	-	-	3	12	1	12	11	11	-	-	-	2	20	-	-
Ni	1	5	0.1	0.7	5	5	1	3	1.3	1.3	1	0.25	1	2	25	-	0.92
Pb	1	4	0.1	1	1	4	1	4	3.2	2	1	1	1	2	20	10	0.34
Sb	5	33	-	-	12	12	5	12	12	10	-	-	-	1	12	-	-
Zn	-	2.3	0.1	1.5	3.8	3.8	1	3	13	13	0.75	7.5	0.75	2	13	5	0.97
Chloride	4	6.3	0.55	11	4	14	1	3	13	6.3	3.1	2.5	13	2	63	-	0.16
Sulphate	5	10	0.89	14	5.9	18	1.2	10	10	5	6	2.5	20	2	20	-	0.046

HP 10 if the total content of Pb (neglecting its metallic form or as an alloy) exceeds 3,500 mg/kg. Special concern is raised regarding the HP 14 criterion since *Council Regulation (EU) 2017/997* came into force (EU, 2017). It is feared that great effort is necessary for assessing the HP 14 criterion and that certain waste types could suddenly be classified as hazardous waste under this criterion (Aldrian, 2018; Wahlström et al., 2016). Assessing HP 14 can be done using a summation (calculation) method and/or using bioavailability tests (Klymko et al., 2017; EU, 2017; Planchon et al., 2015). So far no harmonised standard is defined at EU level for carrying out these bio-tests (Republic of Austria, 2018).

The Waste Framework Directive presents an End-of-Waste (EoW) option for certain waste materials that have undergone a recovery operation and meet certain criteria to change status from being a waste to become a product (EU, 2008; EU, 2018). The intention of these EoW criteria is to incentivise recycling, ensure legal security when using such a material and to remove administrative burdens (EU, 2008). All of this under the premise of a high level of environmental protection and an economic benefit from commercialising this material. EoW status for a waste may be obtained at EU level, at national level and from case-to-case within EU member states. At EU level, EoW status has been given to certain scrap metals (EU, 2011, 2013) and glass cullet (EU, 2012). It has been suggested that, perhaps IBA could obtain EoW status, but this has not happened at EU level. A European EoW regulation for IBA might be unfeasible because of the rather complex discussions on how to fulfil the conditions mentioned in Article 6 of the Waste Framework Directive (2008/98/EC (EU, 2008) as amended by Directive (EU) 2018/851 (EU, 2018)), particularly those related to the protection of health and environment. A possible national EoW status for IBA should also not lead to the presumption that this material is inherently safe and that no further testing of the (leaching) properties would be needed. On the contrary, for any accepted application of a secondary material, testing is crucial to show acceptable emissions from this material. So far, none of the EU member states have implemented national EoW regulations specifically addressing IBA (Velzeboer and Van Zomeren, 2017). There would be obvious regulatory problems associated with IBA having EoW status in one country but still being classified as a waste in other countries. In addition, achievement of EoW status of aggregates such as MIBA would change the regulatory regime from waste legislation to product legislation which generally is much less developed in terms of environmental protection than waste legislation (with the Netherlands as the only exception). The UK Environment Agency has decided not to develop national EoW criteria for IBA, but several IBA processing companies in the UK have created a code of practice for reclassifying waste IBA to a secondary raw material by reaching the EoW status (MIBAA, 2017). Their approach is based on guidelines proposed by the UK Environment Agency (United Kingdom, 2014). This guidance can be applied if no EU EoW Regulation applies to this waste material.

4. Conclusion

The present study provides an overview of the legal framework for MIBA utilisation in the European Union, Norway and Switzerland. The hypothesis that these requirements vary significantly within Europe can be confirmed. Even though this issue was already addressed more than a decade ago, hardly anything changed since then and countries are still regulating the utilisation of MIBA individually. Some countries have guidelines in place; others passed laws (regulations, decrees, orders etc.) and in the case of Portugal, authorities decide individually case by case. Laws are leg-

ally binding, whereas guidelines or even individual decisions may leave more room for interpretation and could provide therefore less legal security when using MIBA as secondary construction material. Still, no correlation is found between the level of legal security and the utilisation rate.

As a result, it can be concluded that even though the legal security is an important point when it comes to recycling of MIBA, it does not seem to be the most crucial factor that influences the rate of utilisation. First, if policy is not only providing the possibility for MIBA utilisation, but restricts landfill, it will result in increased utilisation rates due to the recycling obligation. And second, if disposing of MIBA in landfills is economically more attractive than recycling this material, there is only little incentive for a company to first costly process this secondary material for improving its quality, in order to compete with cheap primary material. Therefore, restriction of landfilling can help to stimulate the recycling market.

Since this manuscript focuses on the legal framework of MIBA utilisation, the following main points for a uniform regulatory framework at EU level are proposed: (1) Definition of fields of application. Applications as road foundation layers, embankments etc.; (2) Definition of parameters and requirements that have to be tested with respect to the field of application; (3) A uniform assessment system for establishing limit values – both total and leaching content (e.g. a risk based assessment, rather than adopting existing limit values from other legislation). It is important to note that the limit values will probably differ between countries as a result of the local differences in soil types, groundwater depths and climatic conditions; (4) Standardised test methods – especially for determining the leaching behaviour;

A uniform regulatory framework ensures that the quality of this secondary raw material meets the same high level of environmental protection in all member states. To facilitate the acceptance of MIBA applications, end-of-waste criteria could in theory be defined either at national level or on EU level. However, the feasibility of European EoW criteria for MIBA is probably low due to the country specific situations. Instead European-wide conditions for the use of MIBA resembling those stipulated in Article 6 of the Waste Framework Directive could possibly be harmonised within the waste legislation. The eight EU member states in which waste incineration is not yet established can benefit from a clear regulation, as residue management is an important factor in the planning of an incinerator. If there are already clear rules on EU level, which qualities MIBA must meet for utilisation, this can already be taken into account during the planning phase of an installation. In terms of the HP 14 criterion, clarity should be achieved from the EU or from national governments. As long as there are no clear instructions for assessing HP 14 and chances are that MIBA is suddenly classified as hazardous, there will always be a certain reservation to use this material for construction purposes.

Assuming from 100 wt% of initial IBA, 80 wt% of MIBA is produced (cf. introduction) and these entire 80 wt% could theoretically be used as aggregates in the construction sector, only 0.6 wt% of the primary production of aggregates in the EU could be substituted (EU, 2017). Hence, the overall resource relevance of utilising minerals present in IBA is quite limited. Nonetheless, utilising the mineral fraction could reduce the overall volume of landfills for non-hazardous waste required in the EU by 5 million m³ or 7–8 vol% each year (cf. chapter 3 in supplementary information). And even though the EU's action plan for the circular economy, does not explicitly address residues from waste incineration, using anthropogenic resources like IBA more efficiently in combination with high environmental standards, may contribute to reach the

goals defined in this action plan and helps to close a gap in this circular economy loop.

Acknowledgements

This article/publication is based upon work from COST Action Mining the European Anthroposphere (MINEA), supported by COST (European Cooperation in Science and Technology). The work presented is part of a large-scale research initiative on anthropogenic resources (Christian Doppler Laboratory for Anthropogenic Resources). The financial support of this research initiative by the Federal Ministry of Digital, Business and Enterprise and the National Foundation for Research, Technology and Development is gratefully acknowledged. Industry partners co-financing the research centre on anthropogenic resources are Altstoff Recycling Austria AG (ARA), Borealis group, voestalpine AG, Wien Energie GmbH, Wiener Kommunal-Umweltschutzprojektgesellschaft GmbH (WKU), and Wiener Linien GmbH & Co KG.

The support of the following persons for data acquisition is gratefully acknowledged (in alphabetic order): Lorien Luyckx (Belgium), Patrick Christophory (Luxembourg) and Britta Gausen-Freidl (Switzerland).

Appendix A. Supplementary material

Supplementary data to this article can be found online at <https://doi.org/10.1016/j.wasman.2019.11.031>.

References

- Aldrian, A., 2018. HP 14 – And now what?. *J. Environmen. Waste Manage. Recycl.* 1. <http://www.alliedacademies.org/articles/hp-14-and-now-what-10161.html>.
- Allegrini, E., Maresca, A., Olsson, M.E., Holtze, M.S., Boldrin, A., Astrup, T.F., 2014. Quantification of the resource recovery potential of municipal solid waste incineration bottom ashes. *Waste Manage.* 34, 1627–1636. <https://doi.org/10.1016/j.wasman.2014.05.003>.
- Alwast, H., Riemann, A., 2010. Verbesserung der umweltrelevanten Qualitäten von Schlacken aus Abfallverbrennungsanlagen. Umweltbundesamt, Germany. <https://www.umweltbundesamt.de/sites/default/files/medien/461/publikationen/4025.pdf>.
- Bogush, A., 2018. Anna Bogush, Department of Earth Sciences, University College London and Centre for Agroecology, Water and Resilience, Coventry University. Personal communication (email) on 18th September 2018. Excel file: Waste -to-Energy Plants in Europe (2016–2017).
- Born, J.-P., 2018. Mining Incinerator Bottom Ash for heavy Non-Ferrous Metals and Precious Metals. In: Holm, O., Thome-Kozmiensky, E. (Eds.), *Removal, Treatment and Utilisation of Waste Incineration Bottom Ash*. TK Verlag, Neuruppin Germany, pp. 53–62.
- Brunner, P.H., Rechberger, H., 2015. Waste to energy – key element for sustainable waste management. *Waste Manage.* 37, 3–12. <https://doi.org/10.1016/j.wasman.2014.02.003>.
- Buchholz, T., Luzadis, V.A., Volk, T.A., 2009. Sustainability criteria for bioenergy systems: results from an expert survey. *J. Cleaner Prod.* 17, S86–S98. <https://doi.org/10.1016/j.jclepro.2009.04.015>.
- Bunge, R., 2018. Recovery of Metals from Waste Incineration Bottom Ash. In: Holm, O., Thome-Kozmiensky, E. (Eds.), *Removal, Treatment and Utilisation of Waste Incineration Bottom Ash*, p. 63.
- CEWEP, 2016. Bottom Ash Factsheet. Belgium, Brussels. <http://www.cewep.eu/2017/09/08/bottom-ash-factsheet/>. (accessed. 07 November 2018).
- CEWEP, 2018. Waste-to-Energy Plants in Europe in 2016 – last update 22.10.2018.
- Chandler, A.J., Eighmy, T.T., Hartlen, J., Hjelmar, O., Kosson, D.S., Sawell, S.E., van der Sloot, H.A., Vehlow, J., 1997. Municipal Solid Waste Incinerator Residues: An international perspective on characterisation and management of residues from municipal solid waste incineration. *Elsevier Science, Amsterdam*.
- Chimenos, J.M., 2018. Josep Maria Chimenos, Universitat de Barcelona UB, Department of Materials Science and Physical Chemistry, Personal communication (meeting) on 2nd October 2018. Excel File: Waste-to-Energy Plants in Europe (2016–2017).
- Chimenos, J.M., Segarra, M., Fernández, M.A., Espiell, F., 1999. Characterization of the bottom ash in municipal solid waste incinerator. *J. Hazard. Mater.* 64, 211–222. [https://doi.org/10.1016/S0304-3894\(98\)00246-5](https://doi.org/10.1016/S0304-3894(98)00246-5).
- rillesen, K., Skaarup, J., 2006. Management of Bottom Ash from WTE Plants – An overview of management options and treatment methods. Report by ISWA Working. Group Thermal Treatment. https://www.iswa.org/uploads/tx_iswaknowledgebase/Bottom_ash_from_WTE_2006_01.pdf.
- zech Republic, 2005. Vyhláška č. 294/2005 Sb. English translation: Decree of 11th July 2005 on the conditions of depositing waste in landfills and its use on the surface of the ground and amendments to Decree no. /2001 Coll. on details of waste management. Ministry of the Environment, Czech Republic <https://www.zakonyprolidi.cz/cs/2005-294>.
- Dou, X., Ren, F., Nguyen, M.Q., Ahamed, A., Yin, K., Chan, W.P., Chang, V.W.-C., 2017. Review of MSWI bottom ash utilization from perspectives of collective characterization, treatment and existing application. *Renew. Sustain. Energy Rev.* 79, 24–38. <https://doi.org/10.1016/j.rser.2017.05.044>.
- EN, 2002a. EN 12457-1:2002 – Characterisation of waste – Leaching – Compliance test for leaching of granular waste materials and sludges – Part 1: One stage batch test at a liquid to solid ratio of 2 l/kg for materials with high solid content and with particle size below 4 mm (without or with size reduction).
- EN, 2002b. EN 12457-2:2002-09 – Characterisation of waste – Leaching; Compliance test for leaching of granular waste materials and sludges – Part 2: One stage batch test at a liquid to solid ratio of 10 l/kg for material with particle size below 4 mm (without or with size reduction).
- EN, 2002c. EN 12457-4:2002 – Characterisation of waste – Leaching – Compliance test for leaching of granular waste materials and sludges – Part 4: One stage batch test at a liquid to solid ratio of 10 l/kg for materials with particle size below 10 mm (without or with size reduction).
- EN, 2003. EN 12457-3:2003-01 – Characterization of waste – Leaching; Compliance test for leaching of granular waste materials and sludges – Part 3: Two stage batch test at a liquid to solid ratio of 2 l/kg and 8 l/kg for materials with high solid content with particle size below 4 mm (without or with size reduction). German version EN 12457-3, 2002.
- EN, 2014. prEN 16637-2:2014 – Construction products – Assessment of release of dangerous substances – Part 2: Horizontal dynamic surface leaching test (CEN/TS 16637-2:2014).
- EN, 2016. prEN 16637-3:2016 – Construction products – Assessment of release of dangerous substances – Part 3: Horizontal up-flow percolation test.
- EU, 2003. Council decision of 19 December 2002 establishing criteria and procedures for the acceptance of waste at landfills pursuant to Article 16 of and Annex II to Directive 1999/31/EC. European Council. <https://eur-lex.europa.eu/LexUriServ/LexUriServ.do?uri=OJ:L:2003:011:0027:0049:EN:PDF>.
- EU, 2004. Regulation (EC) No 850/2004 of the European Parliament and of the Council of 29 April 2004 on persistent organic pollutants and amending Directive 79/117/EEC. European Parliament and the Council. <https://eur-lex.europa.eu/legal-content/EN/TXT/PDF/?uri=CELEX:32004R0850&from=GA>.
- EU, 2010. Directive 2010/75/EU of the European Parliament and of the Council of 24 November 2010 on industrial emissions (integrated pollution prevention and control) Text with EEA relevance. European Parliament and the Council of the European Union.
- EU, 2008. Directive 2008/98/EC of the European Parliament and of the Council of 19 November 2008 on waste and repealing certain Directives (Text with EEA relevance). European Commission. <http://data.europa.eu/eli/dir/2008/98/oj>.
- Council Regulation (EU) No 333/2011 of 31 March 2011 establishing criteria determining when certain types of scrap metal cease to be waste under Directive 2008/98/EC of the European Parliament and of the Council. European Council <https://eur-lex.europa.eu/legal-content/EN/TXT/?uri=CELEX:32011R0333> Council. European Council. (accessed. 27 February 2019).
- EU, 2012. Commission Regulation (EU) No 1179/2012 of 10 December 2012 establishing criteria determining when glass cullet ceases to be waste under directive 2008/98/EC of the European Parliament and of the Council. European Commission. <https://eur-lex.europa.eu/legal-content/EN/TXT/PDF/?uri=CELEX:32012R1179>, (accessed. 27 February 2019).
- Commission regulation (EU) No 715/2013 of 25 July 2013 establishing criteria determining when copper scrap ceases to be waste under Directive 2008/98/EC of the European Parliament and of the Council. European Commission <https://eur-lex.europa.eu/legal-content/EN/TXT/PDF/?uri=CELEX:32013R0715> Council. European Commission. (accessed. 27 February 2019).
- EU, 2014a. Commission decision of 18 December 2014 amending Decision 2000/532/EC on the list of waste pursuant to Directive 2008/98/EC of the European Parliament and of the Council (Text with EEA relevance) (2014/955/EU), 2014/955/EU. European Commission.
- EU, 2014b. Commission Regulation (EU) No 1357/2014 of 18 December 2014 replacing Annex III to Directive 2008/98/EC of the European Parliament and of the Council on waste and repealing certain Directives Text with EEA relevance, No 1357/2014. European Commission.
- EU, 2017. Study on the review of the list of Critical Raw Materials – Non-critical Raw Materials Factsheets. European Commission, Luxembourg.
- EU, 2017a. Council Regulation (EU) 2017/997 of 8 June 2017 amending Annex III to Directive 2008/98/EC of the European Parliament and of the Council as regards the hazardous property HP 14 ‘Ecotoxic’ (Text with EEA relevance.), 2017/997. European Commission. <http://data.europa.eu/eli/reg/2017/997/oj>.
- EU, 2018. Directive (EU) 2018/851 of the European Parliament and of the Council of 30 May 2018 amending Directive 2008/98/EC on waste (Text with EEA relevance), 2018/851 European Parliament and the Council. <http://data.europa.eu/eli/dir/2018/851/oj>.
- EU, 2019. Regulations, Directives and other acts. EU law. European Union. European Industrial Relations Dictionary – Definition of Soft law by European Foundation for the Improvement of Living and Working Conditions. Working

- Conditions <https://www.eurofound.europa.eu/observatories/eurwork/industrial-relations-dictionary/soft-law>.
- Fagerqvist, J., 2019. Johan Fagerqvist, Avfall Sverige, Personal communication (email) on 29th March 2019.
- Flemish Government, 2012. VLAREMA - 17 FEBRUARY 2012. – Order of the Government of Flanders adopting the Flemish regulation on the sustainable management of material cycles and waste. Government of Flanders, Belgium, Flanders. <https://navigator.emis.vito.be/mijn-navigator?wold=44096>.
- French Republic, 2011. Arrêté du 18 novembre 2011 relatif au recyclage en technique routière des mâchefers d'incinération de déchets non dangereux, France.
- Gabre-Madhin, E.Z., Haggblade, S., 2004. Successes in African agriculture: results of an expert survey. *World Dev.* 32, 745–766. <https://doi.org/10.1016/j.worlddev.2003.11.004>.
- Generalitat de Catalunya, 1995. Diari Oficial de la Generalitat de Catalunya, Núm. 2181-13.3.1996, Ordre de 15 de febrer de 1996, sobre valorització d'escòries, Departament de medi ambient, Spain.
- Göknelma, M., Meling, I., Soyulu, E., Kvithyld, A., Tranell, G., 2019. A Method for Assessment of Recyclability of Aluminum from Incinerated Household Waste. Springer International Publishing, Cham, pp. 1359–1365.
- Government of Finland, 2017. Government Decree on the Recovery of Certain Wastes in Earth Construction (843/2017). Ministry of the Environment, Finland.
- Government of the Netherlands, 2007. Regeling van 13 december 2007, nr. DJZ2007124397, houdende regels voor de uitvoering van de kwaliteit van de bodem. (English: Regulation of 13 December 2007, no. DJZ2007124397, laying down rules for the implementation of soil quality.), The Minister of Housing Spatial Planning and the Environment and the State Secretary for Transport Public Works and Water Management, The Netherlands.
- Government of Wallonia, 2001. "Arrêté du Gouvernement wallon" dated 14/06/2001 (latest modification on 05/07/2018). Wallonia, Belgium.
- Holm, O., Simon, F.-G., 2017. Innovative treatment trains of bottom ash (BA) from municipal solid waste incineration (MSWI) in Germany. *Waste Manage.* 59, 229–236. <https://doi.org/10.1016/j.wasman.2016.09.004>.
- Huber, F., Blasenbauer, D., Aschenbrenner, P., Fellner, J., 2019. Complete determination of the material composition of municipal solid waste incineration bottom ash. *Waste Manage.* 102, 677–685. <https://doi.org/10.1016/j.wasman.2019.11.036>.
- Huber, F., Fellner, J., 2018. Quality criteria for the utilisation of mswi bottom ash in europe, SUM2018. CISA Publisher, Italy, Congress Center Giovanni XXIII, Bergamo, Italy, Fourth Symposium on Urban Mining.
- Hykš, J., 2016. Danish experience with utilisation of bottom ash in road constructions: system overview, Workshop on Technologies and Data for Material Recovery from Waste Incineration Residues in Europe.
- Italian Republic, 1998. Decreto 5 febbraio 1998 - (Supplemento ordinario alla Gazzetta ufficiale 16 aprile 1998 n. 88) Individuazione dei rifiuti non pericolosi sottoposti alle procedure semplificate di recupero ai sensi degli articoli 31 e 33 del decreto legislativo 5 febbraio 1997, n. 22 (versione coordinata con il DM 5 aprile 2006). Il Ministro dell'ambiente, Italy.
- Italian Republic, 2006. Decreto 5 aprile 2006, n. 186. Regolamento recante modifiche al decreto ministeriale 5 febbraio 1998 "Individuazione dei rifiuti non pericolosi sottoposti alle procedure semplificate di recupero, ai sensi degli articoli 31 e 33 del decreto legislativo 5 febbraio 1997, n. 22" (Regulatory that modified Ministerial Decree dated 5 February 1998). Official Gazette n. 115 dated 19 May 2006, Italy. http://www.gazzettaufficiale.it/atto/serie_generale/caricaDettaglioAtto/originario?atto.dataPubblicazioneGazzetta=2006-05-19&atto.codiceRedazionale=006G0202&elenco30giorni=false.
- Kahle, K., Kamuk, B., Kallesøe, J., Fleck, E., Lamers, F., Jacobsson, L., Sahlén, J., 2015. Bottom Ash from WTE Plants – Metal Recovery and Utilization. Report by ISWA Working Group on Energy Recovery.
- Kingdom of Denmark, 2016. BEK nr 1672 af 15/12/2016. Bekendtgørelse om anvendelse af restprodukter, jord og sorteret bygge- og anlægssaffald, Denmark.
- Klymko, T., Dijkstra, J.J., Van Zomeren, A., 2017. Guidance document on hazard classification of MSWI bottom ash. ECN, The Netherlands.
- LAGA, 1994. Merkblatt der Landesarbeitsgemeinschaft Abfall für die Entsorgung von Abfällen aus Verbrennungsanlagen für Siedlungsabfälle. Mitteilungen der Länderarbeitsgemeinschaft Abfall (M19). Schmidt Verlag, Berlin, Erich.
- LAGA, 1995. Anforderungen an die stoffliche Verwertung von mineralischen Reststoffen/Abfällen - Technische Regeln - Mitteilungen der Länderarbeitsgemeinschaft Abfall (M20). Schmidt Verlag, Berlin, Erich.
- Lamers, F., 2015. Treatment of Bottom Ashes of Waste-to-Energy Installations – State of the Art, Mineralische Nebenprodukte und Abfälle 2. TK Verlag, Neuruppin, Germany.
- Lederer, J., Šyc, M., Biganzoli, L., Bogush, A., Bontempi, E., Braga, R., Costa, G., Funari, V., Grosso, M., Hyks, J., Kameníková, P., Quina, M.M.J., Rasmussen, E., Schlumberger, S., Simon, F.-G., Weibel, G., 2018. Mining the European Anthroposphere (MINEA). Report by working group 3: Resource potential of solid residues from waste incineration. Deliverable 3.1 – Recovery technologies for waste incineration residues.
- Lederer, J., Šyc, M., Bogush, A., Fellner, J., 2017. A network approach towards a secondary raw material inventory for europe applied to waste incineration residues., Sardinia 2017 – Sixteenth International Waste Management and Landfill Symposium. CISA Publisher, Italy, S. Margherita di Pula, Cagliari, Italy.
- Lithuanian Government, 2016. ĮSAKYMAS – dėl atliekų deginimo įrenginiuose ir bendro atliekų deginimo įrenginiuose susidariusių pelenų ir šlako tvarkymo reikalavimų patvirtinimo - 2016 m. lapkričio 25 d. Nr. D1-805, Ministry of the Environment, Vilnius, Lithuania.
- Liu, A., Ren, F., Lin, W.Y., Wang, J.-Y., 2015. A review of municipal solid waste environmental standards with a focus on incinerator residues. *Int. J. Sustain. Built Environ.* 4, 165–188. <https://doi.org/10.1016/j.ijsbe.2015.11.002>.
- Mesters, K., 2018. Rahmenbedingung für den Einsatz von Hausmüllverbrennungsaschen im Bauwesen – Technische und umweltrelevante Regelungen (English: Framework Conditions for the use of Incineration Bottom Ash in Construction - Technical and Environmental Regulations), Mineralische Nebenprodukte und Abfälle 5 – Aschen, Schlacken. Thomé-Kozmiensky Verlag GmbH, Germany, Stäube und Baurestmassen.
- Meuser, M., Nagel, U., 2009. The Expert Interview and Changes in Knowledge Production. In: Bogner, A., Littig, B., Menz, W. (Eds.), *Interviewing Experts*. Palgrave Macmillan UK, London, pp. 17–42.
- MIBAA, 2017. Manufacturers of IBA Aggregates Association., MIBAA, United Kingdom. <http://mibaa.org.uk/index.html>. (accessed, United Kingdom 6 November 2018).
- MINEA, 2019. Mining the European Anthroposphere (MINEA) Mining the European Anthroposphere. Austria MINEA, Vienna, Austria. <http://www.minea-network.eu/index.phpVienna>. (accessed, 24 May 2019).
- Morf, L.S., Brunner, P.H., Spaun, S., 2000. Effect of operating conditions and input variations on the partitioning of metals in a municipal solid waste incinerator. *Waste Manage. Res.* 18, 4–15. <https://doi.org/10.1177/0734242X0001800102>.
- Naturvårdsverket, 2010. Atervinning av avfall i anläggningsarbeten – Handbok. Naturvårdsverket, Sweden.
- NEN, 2004. NEN 7375:2004 nl - Leaching characteristics - Determination of the leaching of inorganic components from moulded or monolithic materials with a diffusion test - Solid earthy and stony materials, The Netherlands.
- Nørgaard, K.P., Hyks, J., Mulvad, J.K., Frederiksen, J.O., Hjelmar, O., 2019. Optimizing large-scale ageing of municipal solid waste incinerator bottom ash prior to the advanced metal recovery: Phase I: Monitoring of temperature, moisture content, and CO2 level. *Waste Manage.* 85, 95–105. <https://doi.org/10.1016/j.wasman.2018.12.019>.
- OECD, 2019. Regulatory policy – Definition of soft law by the Organisation for Economic Co-operation and Development. OECD, <https://www.oecd.org/gov/regulatory-policy/irc10.htm>.
- Onwuegbuzie, A.J., Dickinson, W.B., Leech, N.L., Zoran, A.G., 2009. A Qualitative Framework for Collecting and Analyzing Data in Focus Group Research. *Int. J. Qual. Methods* 8, 1–21. <https://doi.org/10.1177/160940690900800301>.
- Pajak, T., 2019. Tadeusz Pajak, AGH University of Science and Technology in Kraków, Department of Power Systems and Environmental Protection Facilities, Personal communication (email) on 8th January 2019.
- Planchon, M., Saïdi, N., Pandard, P., Troise, A., 2015. Study to assess the impacts of different classification approaches for hazard property "HP 14" on selected waste streams - Final report. Prepared for the European Commission (DG ENV), in collaboration with INERIS. BIO by Deloitte.
- Portuguese Republic, 2009. Decreto-Lei n.º 183/2009 de 10 de Agosto. Ministério do ambiente, do ordenamento do território e do desenvolvimento regional, Portugal.
- Rantsi, R., 2018. MSWI BA Utilization in Finland, VDI Conference Metals and Minerals from IBA, Düsseldorf, Germany.
- Ray, L., 1999. Measuring party orientations towards European integration: Results from an expert survey. *Europ. J. Polit. Res.* 36, 283–306. <https://doi.org/10.1023/A:1007009106184>.
- Republic of Austria, 2017a. Bundesabfallwirtschaftsplan 2017 - Teil 1 (Federal Waste Management Plan 2017). Bundesministerium für Nachhaltigkeit und Tourismus.
- Republic of Austria, 2017b. Technische Grundlagen für den Einsatz von Abfällen als Ersatzrohstoffe in Anlagen zur Zementherstellung (English: Technical basics for the use of waste as secondary raw material in cement production.). Federal Ministry of Agriculture, Forestry, Environment and Water Management, Austria.
- Republic of Austria, 2018. Leitfaden des Bundesministeriums für Nachhaltigkeit und Tourismus (BMNT) Bewertung der gefahrenrelevanten Eigenschaft HP 14, ökotoxisch" gemäß Verordnung (EU) 2017/997 des Rates vom 8. juni 2018, in: Federal Ministry for Sustainability and Tourism (BMNT) (Ed.), BMNT, Austria.
- Republic of Poland, 2015. Poz. 796 - Rozporządzenie Ministra Środowiska z dnia 11 maja 2015 r. w sprawie odzysku odpadów poza instalacjami i urządzeniami - English: No. 796 - Ordinance of the Minister of the Environment of May 11, 2015 on the recovery of waste outside installations and equipment, Warsaw, Poland.
- Saveyn, H., Eder, P., Garbarino, E., Muchova, L., Hjelmar, O., van der Sloot, H., Comans, R., van Zomeren, A., Hykš, J., Oberender, A., 2014. Study on methodological aspects regarding limit values for pollutants in aggregates in the context of the possible development of end-of-waste criteria under the EU Waste Framework Directive.
- Silva, R.V., de Brito, J., Lynn, C.J., Dhir, R.K., 2019. Environmental impacts of the use of bottom ashes from municipal solid waste incineration: A review. *Resour. Conserv. Recycl.* 140, 23–35. <https://doi.org/10.1016/j.resconrec.2018.09.011>.
- Swiss Federal Council, 2015. Verordnung über die Vermeidung und die Entsorgung von Abfällen (VVEA), Switzerland.
- Šyc, M., 2018. Michal Šyc, Environmental Process Engineering Laboratory, Institute of Chemical Process Fundamentals of AS CR, Personal communication on 24th September 2018 (2), Word File.

- Tegelbeckers, P., Aubert, A., Jouvenet, A.J., Moulin, I., Tran, L.T., Elhamzaoui, S., 2015. *Qualite et devenir des machefers d'incineration de dechets non dangereux etat des lieux et perspectives*. France, RECORD, p. 134.
- United Kingdom, 2014. Guidance – Turn your waste into a new non-waste product or material. Environment Agency, United Kingdom. <https://www.gov.uk/guidance/turn-your-waste-into-a-new-non-waste-product-or-material#eu-end-of-waste-regulations>. (accessed. 6 November 2018).
- United Kingdom, 2019. Guidance – Use of unbound municipal Incinerator Bottom Ash Aggregate (IBAA) in construction activities: RPS 206. Environment Agency, United Kingdom. <https://www.gov.uk/government/publications/use-of-unbound-municipal-incinerator-bottom-ash-aggregate-ibaa-in-construction-activities-rps-206>. (accessed. 29 January 2019).
- Utilitalia, 2019. *Rapporto sul recupero energetico da rifiuti in Italia*. Report by Utilitalia in collaboration with Istituto Superiore per la Protezione e la Ricerca Ambientale. (ISPRA), Italy.
- Valorsul, 2017. *Relatório & Contas 2017*, Portugal.
- Van Caneghem, J., De Coster, E., Vandenbergh, K., De Broyer, S., Lambrix, N., Weemaels, L., 2019. Closing the household metal packaging cycle through recovery of scrap from waste-to-energy bottom ash: The case study of Flanders. *Resour. Conserv. Recycl.* 144, 115–122. <https://doi.org/10.1016/j.resconrec.2019.01.028>.
- Van Gerven, T., Geysen, D., Stoffels, L., Jaspers, M., Wauters, G., Vandecasteele, C., 2005. Management of incinerator residues in Flanders (Belgium) and in neighbouring countries. A Comparison. *Waste Manage.* 25, 75–87. <https://doi.org/10.1016/j.wasman.2004.09.002>.
- Van Praagh, M., Johansson, M., Fagerqvist, J., Grönholm, R., Hansson, N., Svensson, H., 2018. Recycling of MSWI-bottom ash in paved constructions in Sweden – A risk assessment. *Waste Manage.* 79, 428–434. <https://doi.org/10.1016/j.wasman.2018.07.025>.
- Vehlow, J., Bourtsalas, A.C., 2019. WTE: Management of WTE Residues in Europe. In: Themelis, N.J., Bourtsalas, A.C. (Eds.), *Recovery of Materials and Energy from Urban Wastes: A Volume in the Encyclopedia of Sustainability Science and Technology*, Second Edition. Springer, New York, New York, NY, pp. 159 – 181. <https://doi.org/10.1007/978-1-4939-7850-2>.
- Velzeboer, I., Van Zomeren, A., 2017. *End of Waste criteria for inert aggregates in member states*. ECN, The Netherlands.
- Verbinnen, B., Billen, P., Van Caneghem, J., Vandecasteele, C., 2017. Recycling of MSWI Bottom Ash: A Review of Chemical Barriers, Engineering Applications and Treatment Technologies. *Waste Biomass Valorization* 8, 1453–1466. <https://doi.org/10.1007/s12649-016-9704-0>.
- Wahlström, M., Laine-Ylijoki, J., Wik, O., Oberender, A., Hjelmar, O., 2016. *Hazardous waste classification – Amendments to the European Waste Classification regulation – what do they mean and what are the consequences?* Norden (Nordic Council of Ministers). Denmark, Copenhagen.
- Wood, L.E., Ford, J.M., 1993. Structuring interviews with experts during knowledge elicitation. *Int. J. Intell. Syst.* 8, 71–90. <https://doi.org/10.1002/int.4550080106>.